



# 杭州科德磁业有限公司

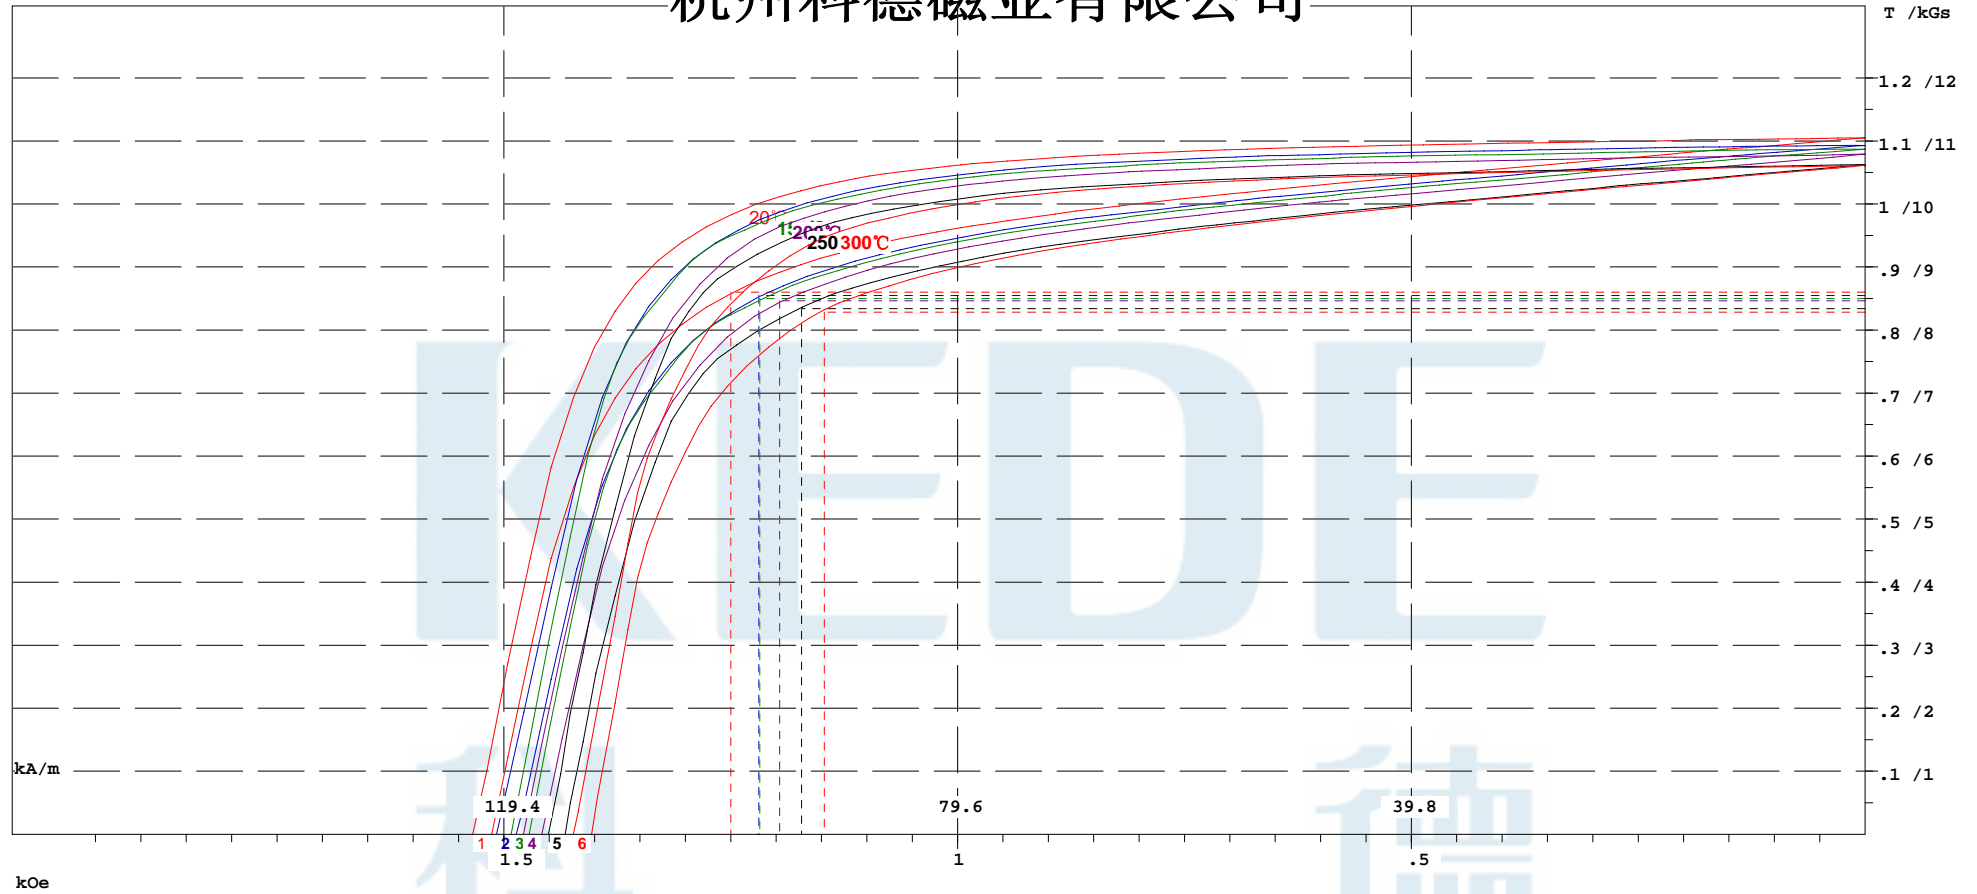

SampleNo	Br (T)	Hcb (kA/m)	Hcj (kA/m)	(BH)max (kJ/m <sup>3</sup> )	Hk (kA/m)	Hd (kA/m)	Bd (T)	Hk/Hcj (%)	Test Date	Sample Shape	S-T (°C)	Size (mm)
<b>1.105</b>	<b>120</b>	<b>122</b>	<b>85.4</b>	<b>98</b>	<b>99</b>	<b>0.860</b>	<b>80.4</b>	<b>2018</b>	<b>Column 20</b>	<b>10.00</b>		
<b>1.093</b>	<b>118</b>	<b>120</b>	<b>82.8</b>	<b>96</b>	<b>97</b>	<b>0.855</b>	<b>79.8</b>	<b>2018</b>	<b>Column 100</b>	<b>10.00</b>		
<b>1.087</b>	<b>117</b>	<b>119</b>	<b>81.7</b>	<b>96</b>	<b>97</b>	<b>0.850</b>	<b>80.6</b>	<b>2018</b>	<b>Column 150</b>	<b>10.00</b>		
<b>1.079</b>	<b>116</b>	<b>118</b>	<b>80.2</b>	<b>94</b>	<b>95</b>	<b>0.846</b>	<b>80.2</b>	<b>2018</b>	<b>Column 200</b>	<b>10.00</b>		
<b>1.063</b>	<b>114</b>	<b>115</b>	<b>77.9</b>	<b>93</b>	<b>93</b>	<b>0.834</b>	<b>80.6</b>	<b>2018</b>	<b>Column 250</b>	<b>10.00</b>		
<b>1.062</b>	<b>112</b>	<b>113</b>	<b>75.7</b>	<b>90</b>	<b>91</b>	<b>0.828</b>	<b>79.6</b>	<b>2018</b>	<b>Column 300</b>	<b>10.00</b>		

**CAINiCo80/12**

# 杭州科德磁业有限公司

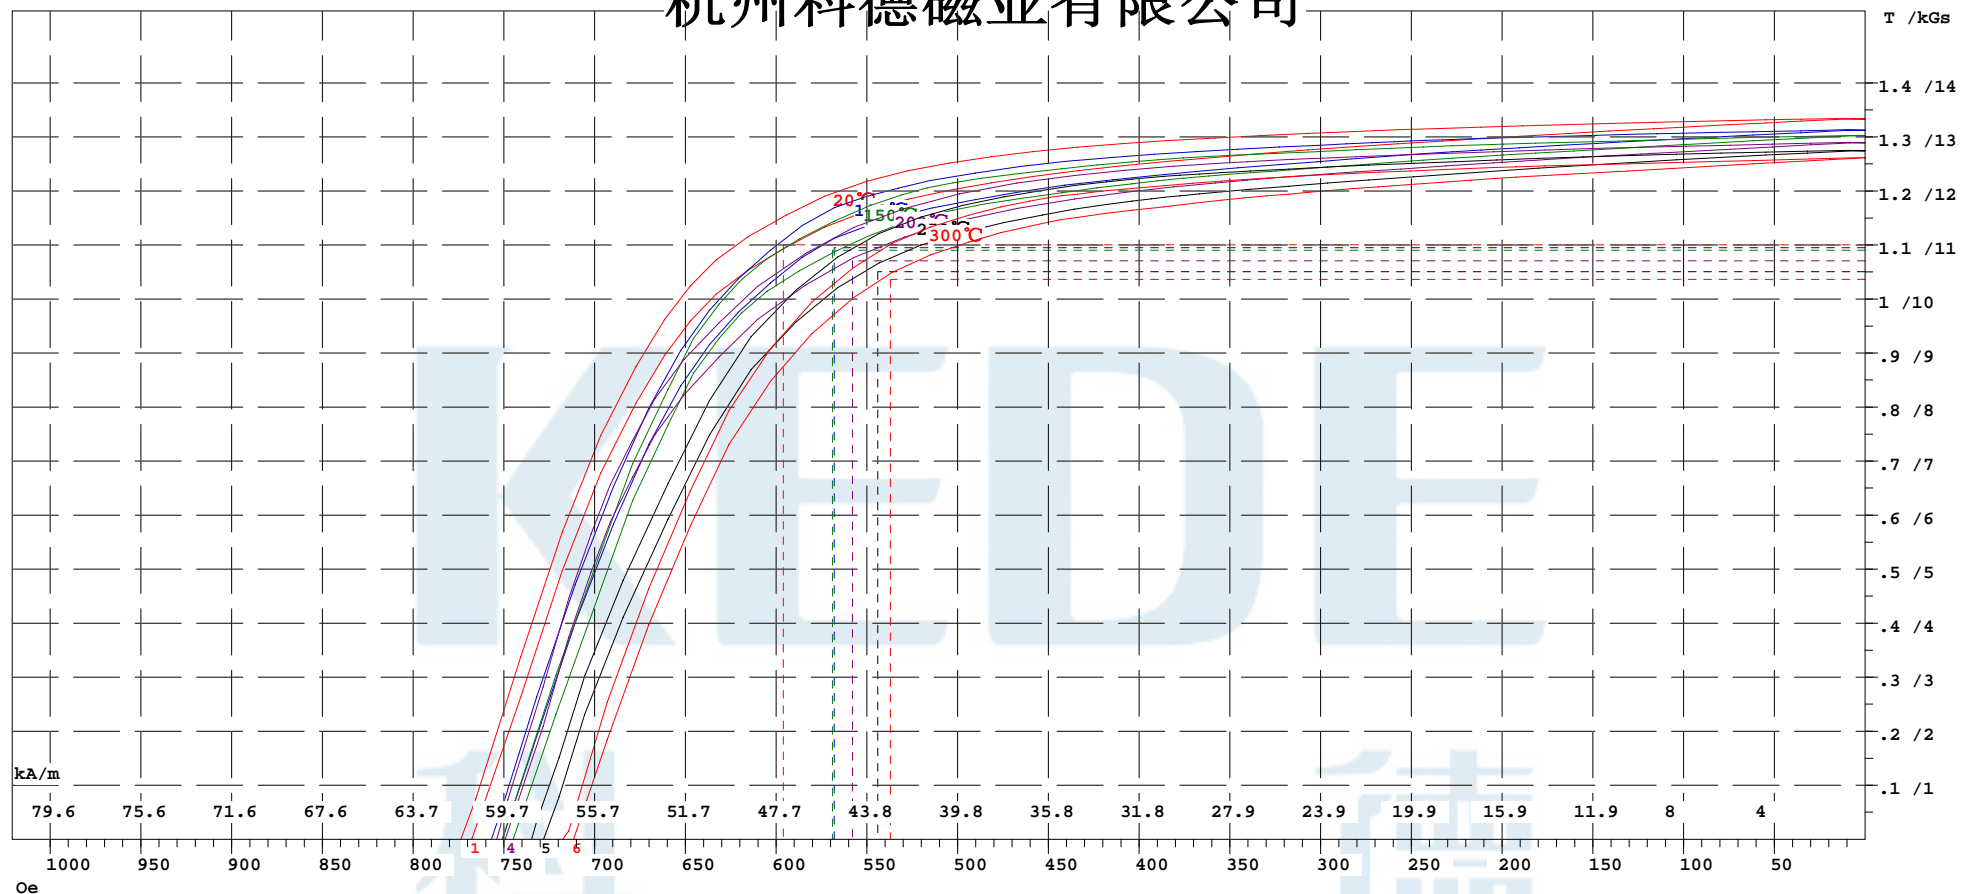

SampleNo	Br (T)	Hcb (kA/m)	Hcj (kA/m)	(BH)max (kJ/m <sup>3</sup> )	Hk (kA/m)	Hd (kA/m)	Bd (T)	Hk/Hcj (%)	Test Date	Sample Shape	S-T (°C)	Size (mm)
<b>CA NiCo52/6</b>	1.335	61.1	61.6	52.0	45.4	47.4	1.100	73.8	2018	Column	20	10.00
	1.314	59.7	60.2	50.0	44.5	45.2	1.095	73.9	2018	Column	100	10.00
	1.303	59.3	59.8	49.2	44.1	45.3	1.090	73.8	2018	Column	150	10.00
	1.291	59.6	60.0	48.3	42.7	44.4	1.071	71.2	2018	Column	200	10.00
	1.276	57.9	58.5	46.1	41.8	43.3	1.051	71.5	2018	Column	250	10.00
	1.262	56.6	57.1	45.0	41.2	42.7	1.036	72.2	2018	Column	300	10.00